

MEMORANDUM

To: M.G. Marietta
From: T.W. Thompson, F.D. Hansen
Date: July 24, 1996
Subject: Long-term Performance of Panel Closures

1. INTRODUCTION

After waste has been emplaced in a panel, closures will be built to restrict flow from the panel during the remainder of the operational phase. These closures will include a length of concrete placed in the panel entries. Although it is not the intent of these closures to restrict flow over the regulatory period of 10,000 years, values for their long-term performance characteristics are required to successfully determine their contribution to overall system performance.

Flow of fluids into or out of the panels will be controlled by the conductance of the panel closure, and of the surrounding disturbed rock zone (DRZ). Performance Assessment (PA) calculations use a constant value for DRZ permeability of 10^{-15} m^2 , a value which is substantiated in the records package for the waste rooms (reference). Consideration of the current panel closure designs indicates that they will maintain their structural integrity for the regulatory period. If this is the case, then the concrete element of the closure system will continue to provide resistance to inward deformation of the surrounding salt, and will prohibit the growth of the DRZ from its initial state. Since the DRZ will not increase during the regulatory period, and may decrease, the assumption of a constant DRZ permeability is reasonable.

The panel closures have been designed to limit the flow of brine and gas between panels during the operational phase, and current designs call for these operational closures to include concrete elements (Figure 1). Although these closures are designed for an operational use, it is expected that they will continue to provide fluid flow restriction during the post-closure phase. The remainder of this memorandum establishes the permeability expectations of the closures, with emphasis on the potential for concrete degradation and increase in permeability. For the purposes of these analyses the concrete elements are taken to have a length of nominally 26 ft (7.9 m) (USDOE, 1996a,b), and to be made of a material chosen so as to be compatible with the environment, such as Salado Mass Concrete (SMC: Sandia, 1996) or a similar mix. Degradation of the concrete may occur by interaction with brine flowing through the plug, or with brines flowing along the plug/salt interface or in the DRZ.

2. CONCRETE PROPERTIES

The initial permeability expected for the concrete panel closures are documented in the materials specification appendix of the Compliance Submittal Design Report (CSDR) (Sandia, 1996) developed for the shaft seal system. In addition to conventional engineering properties, the SMC has well documented permeability characteristics, permeabilities having been determined from field tests (Knowles and Howard, 1996) and laboratory studies (Pfeifle et al., 1996). Figure 2, taken from the CSDR, summarizes the available data, and indicates a permeability for as-placed SMC of between 2×10^{-21} and 1.8×10^{-17} m^2 . For calculations performed in this memorandum a value of 10^{-17} m^2 is used, this being at the high end of the values used by PA for the shaft concrete components, and consistent with other data. For example, data on generic portland cement pastes shows that the permeability of oil field concrete plugs is on the order of 1×10^{-19} m^2 , while data from the Bell Canyon Test indicate permeabilities for borehole concrete plugs of 5×10^{-17} m^2 (Petersen and Christensen, 1980; Christensen and Hunter, 1980).

For the purposes of calculating degradation of the concrete member an assumption of porosity is necessary. The expected value is 5 %, which is higher than the 2% estimated by Petersen and Christensen (1980) for the Bell Canyon Test plugs, but is generally consistent with practical experience of field emplaced concrete structures, and is the value for cast in-place SMC given in the CSDR (Sandia, 1996). An upper limit for porosity is taken as 10%, which is an engineering estimate for concrete.

As noted in the introduction, the concrete closure member is expected to be structurally stable for the regulatory period, and to provide support for the surrounding rock and the DRZ. In this context it can be noted that the unconfined compressive strength of SMC is greater than 4500 psi (30 MPa), and that under the confined state of stress within the closure system the ultimate strength will be greater than this (Pfeifle et al, 1996). This strength is sufficient to preclude structural failure of the concrete member in the panel entries.

3. DEGRADATION OF CONCRETE

The solid matrix that makes up concrete is composed almost entirely of amorphous to cryptocrystalline solid phases. These phases are thermodynamically unstable, and with time and exposure to water they alter into more stable and more crystalline assemblages. Thermodynamic calculations conducted by Alcorn et al (1992) have predicted the alteration phases of portland cement due to exposure to a variety of waters and brines as including tobermorite, quartz, gypsum, calcite, clays and zeolite, produced at the expense of soluble and unstable materials such as portlandite. The theoretical alteration assemblage occupies more volume than the original solids. These calculated results have been verified by subsequent experiments in which waters and cement were reacted (Onofrei et al., 1992).

At free surfaces concrete materials are not physically supported and can spall. Long term leaching experiments report that surface diffusion controlled alteration is dependent on the C_3A content of the cement and the Mg and SO_4 content of leachant (Walton et al., 1990). Creation of an alteration rind weakens the concrete and makes it subject to spalling (Wakeley et al., 1994). The mechanism for spalling is that the alteration phases occupy more volume than the original

solids, volumetric expansion increases internal pore pressures until concrete tensile strengths are exceeded and spalling occurs. Short-term, empirical studies of ordinary concrete in brine report alteration rates in the range of 0.7 to 1 mm/year (Atkinson and Hearne, 1990) - These rates are likely to be overestimates because diffusion distance varies as the square root of time. Further details are given in Appendix C of Thompson et al., 1996.

4. DEGRADATION OF CONCRETE PANEL CLOSURES

The concrete elements of the panel closures may degrade in one of two ways, either by flow of brines through the mass of the concrete element, or by flow of brines along the interface.

4.1 Flow Through the Concrete Element

An estimate of the degradation of a concrete closure element may be made based on data on the progression of concrete chemical alteration reported by Berner (1990) for both fresh water and brine leachants (Figure 3). The progression is charted in terms of the volume of water flow, and indicates that more than 100 pore volumes of leachants must pass through concrete before there is chemical evidence that the matrix is being attacked. Based on these results, it has been assumed (conservatively) that the concrete closure elements will degrade significantly after 100 pore volumes of water have passed through them. A more detailed discussion of these results is given in Thompson et al. (1996).

This volume can be converted to performance life by using Darcy's Law and considering the flow of fluids through the plug and the surrounding DRZ. If there is a pressure difference between the panel and the rest of the repository, flow will occur through the panel closure and the surrounding DRZ, with the two elements acting as flow resistors in parallel (Figure 4). If the pressure in the panel is P_1 (Pa) and in the rest of repository is P_2 (Pa), then under brine saturated conditions, the steady state flow rate out of the panels will be Q , where:

$$Q = A \cdot (k'/\mu) \cdot (P_1 - P_2) / L \quad \text{m}^3/\text{sec}, \quad (1)$$

where: A is the total flow area of the panel closure plus DRZ (m^2)
 L is the flow length (m)
 μ is the fluid viscosity (Pa.s)
 k' is the composite permeability of the panel closure plus DRZ (m^2).

The composite permeability, k' , is given by:

$$k' = (k_d A_d + k_c A_c) / (A_d + A_c), \quad (2)$$

where: k_d, k_c are the permeabilities of the DRZ and plug closure respectively (m^2)
 A_d, A_c are the flow cross-sectional areas of the DRZ and plug closure respectively (m^2).

The flow through the panel closure, q_c , will be:

$$q_c/Q = k_c A_c / (k_d A_d + k_c A_c). \quad (3)$$

The pore volume of the panel closure (V_p) is:

$$V_p = A_c L \phi \text{ m}^3,$$

where ϕ is the porosity. The number of pore volumes (N_p) flowing through the closure in unit time will be:

$$N_p = q_c / V_p \text{ pore volumes/sec,}$$

and the time for 100 pore volumes to flow through the closure will be:

$$t_{100} = 100 / (N_p * 3.154 \times 10^7) \text{ years}$$

The current design (USDOE, 1996a,b) calls for a length of 7.9 m (26 ft) for the concrete closure, and a cross-sectional area of 39.6 m² (10 m wide by 3.96 m high). As noted in Section 2 an undegraded concrete permeability of 10⁻¹⁷ m², and a porosity ranging from 5% to 10% may be assumed. The DRZ around the closure is assumed to have a permeability of 10⁻¹⁵ m². Based on the BRAGFLO grid (reference) the DRZ may be assumed to have a height of 11.95 m above the closure and 2.23 m below. It is assumed that the DRZ in the pillars at either side of the closure heals due to creep closure onto the rigid concrete. The DRZ flow area may therefore be taken as 141.8 m² (11.95 + 2.23 m high by 10 m wide).

Given these values, the effective permeability of the closure and the DRZ, from equation (2), is 7.84x10⁻¹⁶ m², with an effective flow area of 181.4 m². When brine flows between the panel and the rest of the repository, from equation (3), only 0.28 % will flow through the closure, the remainder (99.72 %) will be through the DRZ.

An analysis of calculations made with BRAGFLO (reference) using a range of parameters, and assuming permeabilities for the closures and DRZ of 10⁻¹⁵ m², indicates that the maximum cumulative flow between the panel and the rest of the repository for any likely E1 or E2 scenario will be of the order of 10⁴ m³ (Figure 5). With these flows, and the slit in flows indicated above, only 28 m³ of brine will flow through the concrete closure in 10,000 years. For a porosity range of 5 % to 10 % the maximum cumulative flow through the concrete closure in 10,000 years will therefore be between 0.6 and 1.2 pore volumes. The same point is made in Figure 6, which shows the cumulative flow with closure permeabilities of 10⁻¹⁵ to 10⁻¹⁷ m². Degradation will be minimal with these flow volumes.

4.2 Flow Along the Interface

Flow along the interface may be more rapid due to the higher permeabilities in the DRZ. A **maximum** effect of this flow might be estimated to be equivalent to the free surface spall rate of 0.5 to 1 mm/yr. Such a degradation rate is unrealistically high, since the degradation will be controlled by the rate of fluid flow, and total loss of material will not occur in a physically constrained region. However this rate of spall is much less than the expected closure rates (measured at the order of 0.1 to 0.2 ft/yr. or 30 to 60 mm/yr in Panel 1: USDOE, 1996b) so even such a rapid spall rate would be more than compensated for by creep of the salt on the closure. It is therefore concluded that the effect of flow along the interface will be minimal. At most it will lead to an insignificant increase in the DRZ flow area.

5. CONCLUSIONS

It is concluded that the potential flow through the concrete closure is nearly two orders of magnitude too small to cause any significant degradation. Degradation caused by flow in the DRZ adjacent to the concrete will be taken up by creep closure. It is therefore concluded that the panel closures will retain their initial permeability in the post-closure phase. If this permeability is 10^{-17} m^2 , then the effective permeability of the DRZ and the closure together will be about $8 \times 10^{-16} \text{ m}^2$. An assumption of a permeability of 10^{-15} m^2 for the closure and the DRZ is reasonable.

It is also concluded that since no significant degradation is expected for the concrete members, these will maintain their structural integrity and will provide a rigid support to prevent growth of the DRZ during the regulatory period.

6. REFERENCES

- Alcorn, S.R., Coons, W.E., Christian-Frear, T.L., and M.G. Wallace, 1992, "Theoretical Investigations of Grout Seal Longevity," Final Report, Stripa Project TR 92-23, SKB, Stockholm, Sweden.
- Atkinson, A., Goult, D.J., and Hearne, J.A., 1985, "An Assessment of the Long-Term Durability of Concrete in Radioactive Waste Management." Materials Research Society Symposium Proceedings: Scientific Basis for Nuclear Waste Management IX, v. 50, pp 239-246.
- Berner, U., 1990, "A Thermodynamic Description of the Evolution of Pore Water Chemistry and Uranium Speciation During the Degradation of Cement," Technical Report 90-12, Paul Scherrer, Villigen, Switzerland.
- Bonen, D., 1996, "Petrographic Analyses of Concrete and Grout Recovered from the WIPP," The Technological Institute, Northwestern University, Interim Report, January 15, 1996, 9pp.
- Christensen, C.L. and Hunter, T.O., (1980) "The Bell Canyon Test Results" SAND80-2414C. Sandia National Laboratory, Albuquerque NM

- Knowles, M.K., and C.L. Howard, 1996, "Small Scale Seal Test Results," Waste Management '96, Tuscon, AZ.
- Onofrei, M., Gray, M., Coons, W.E., and S.R. Alcorn, 1992, "High Performance Cement Based Grout for Use in a Nuclear Waste Disposal Facility," Waste Management, v.12, pp. 133-154.
- Petersen, E.W., and Christensen, C.L. (1980) "Analysis of Bell Canyon Test Results" SAND80-7044C. Sandia National Laboratories, Albuquerque NM
- Pfeifle, T.W., F.D. Hansen, and M.K. Knowles, 1996. "Salt-Saturated Concrete Strength and Permeability," 4th. Materials Engineering Conference, ASCE, Washington, D.C.
- Sandia National Laboratories, Repository Isolation Department, 1996. "Compliance Submittal Design Report," Sandia National Laboratories, Department 6121, Albuquerque, NM
- Thompson, T.W., W.E. Coons, J.L. Krumhansl, and F.D. Hansen, 1996. "Inadvertent Intrusion Borehole Permeability," Memorandum of Record, July 8, 1996, Sandia National Laboratories, Albuquerque, NM.
- Wakeley, L.D., Poole, T.S., and Burkes, J.P., 1994, "Durability of concrete materials in high-magnesium brines," SAND 93-7073
- Wakeley, L.D., P.T. Harrington, and F.D. Hansen, 1995, "Variability in Properties of Salado Mass Concrete," SAND94-1495, Sandia National Laboratories, Albuquerque, NM.
- Walton, J.C., Plansky, L.E., and Smith, R.W., 1990, "Models for estimation of service life of concrete barriers in low-level waste repositories," NUREG/CR-5542
- U.S. DOE (Department of Energy), 1995, "Waste Isolation Pilot Plant Sealing System Design Report," DOE/WIPP-95-3117.
- U.S. DOE (Department of Energy), 1996a, "Detailed Design Report for an Operational Phase Panel-Closure System," DOE/WIPP-96-2150.
- U.S. DOE (Department of Energy), 1996b, "Final No Migration Variance Petition," DOE/CAO-96-2160.

BRAGFLO grid (ref)

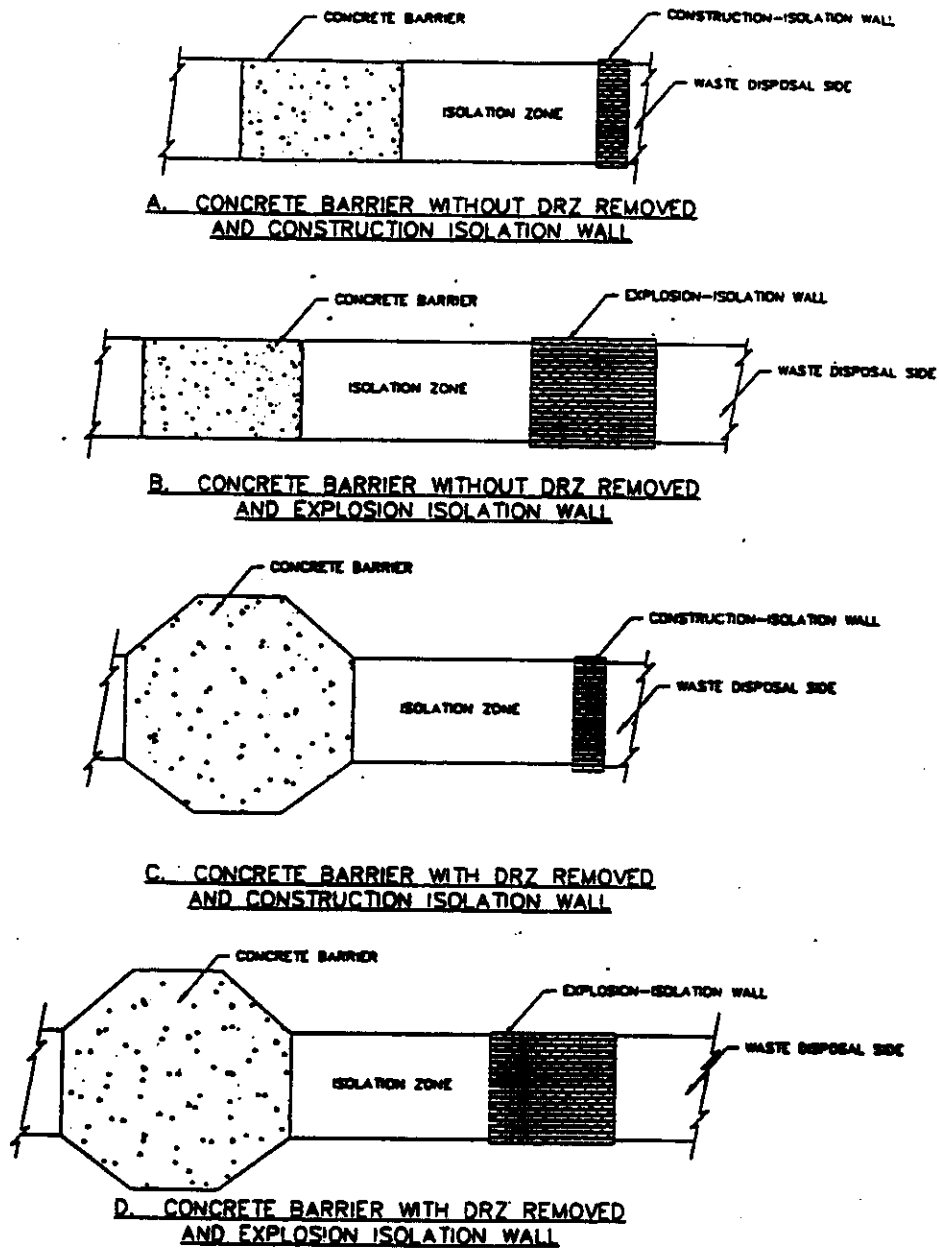


Figure 1: Panel Closure Designs (after USDOE, 1996a)

Draft WIPP Shaft Seal System Compliance Submittal Design Report
Appendix A

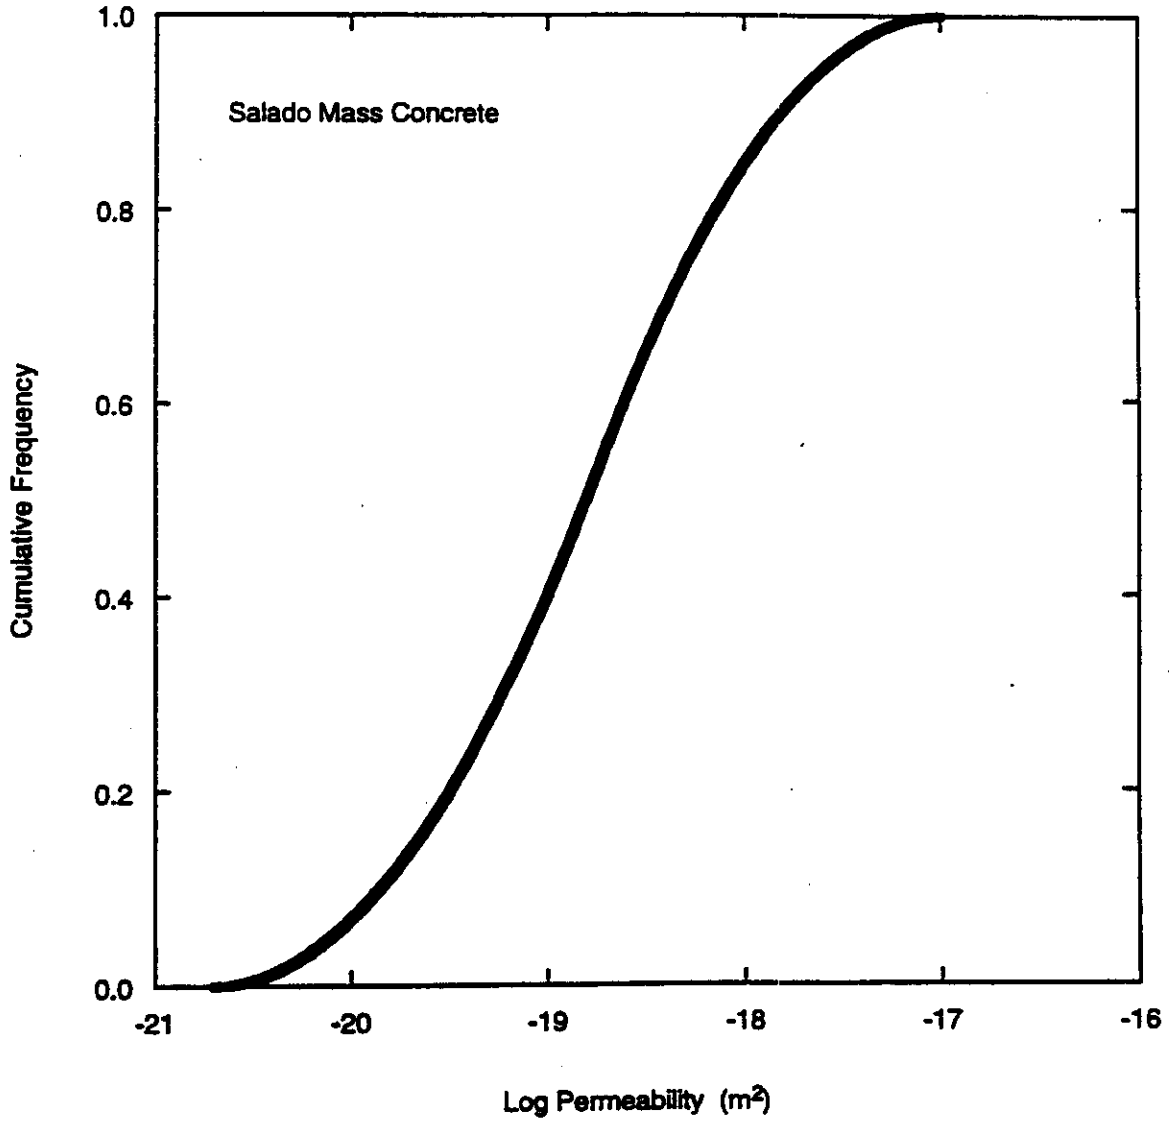


Figure 2: Cumulative Distribution Function for Permeability of SMC (after Sandia, 1996)

Figure c-3 Degradation of "HTS" in standard marl groundwater "MAR". After 6650 cycles calcite is the only solid phase present (T = 25 °C).

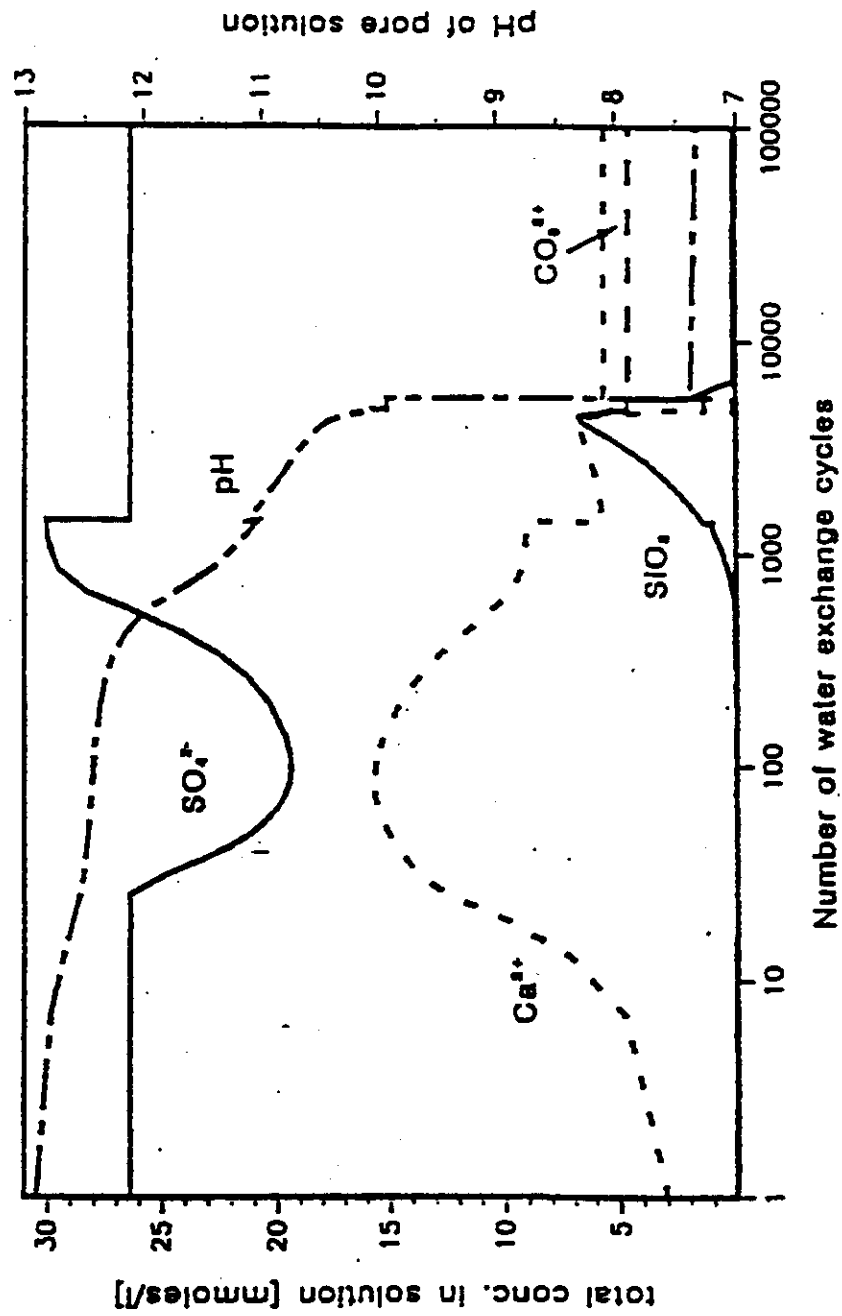


Figure 3: Degradation of Concrete in Brine (after Berner, 1990)

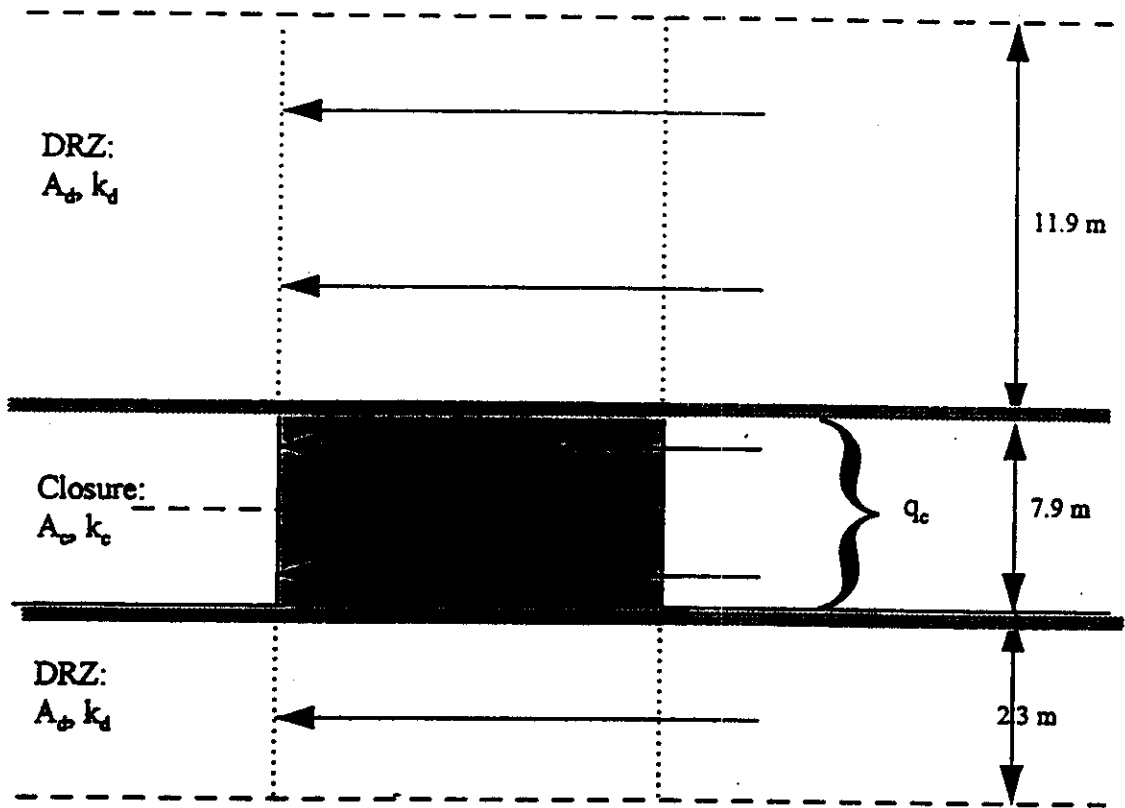


Figure 4: Parallel Flow through the Panel Closure and DRZ

SNL WIPP PA96: BRAGFLO SIMULATIONS (CCA R1 S3)

Cumulative Brine Flow across Panel Seal out of Waste Panel

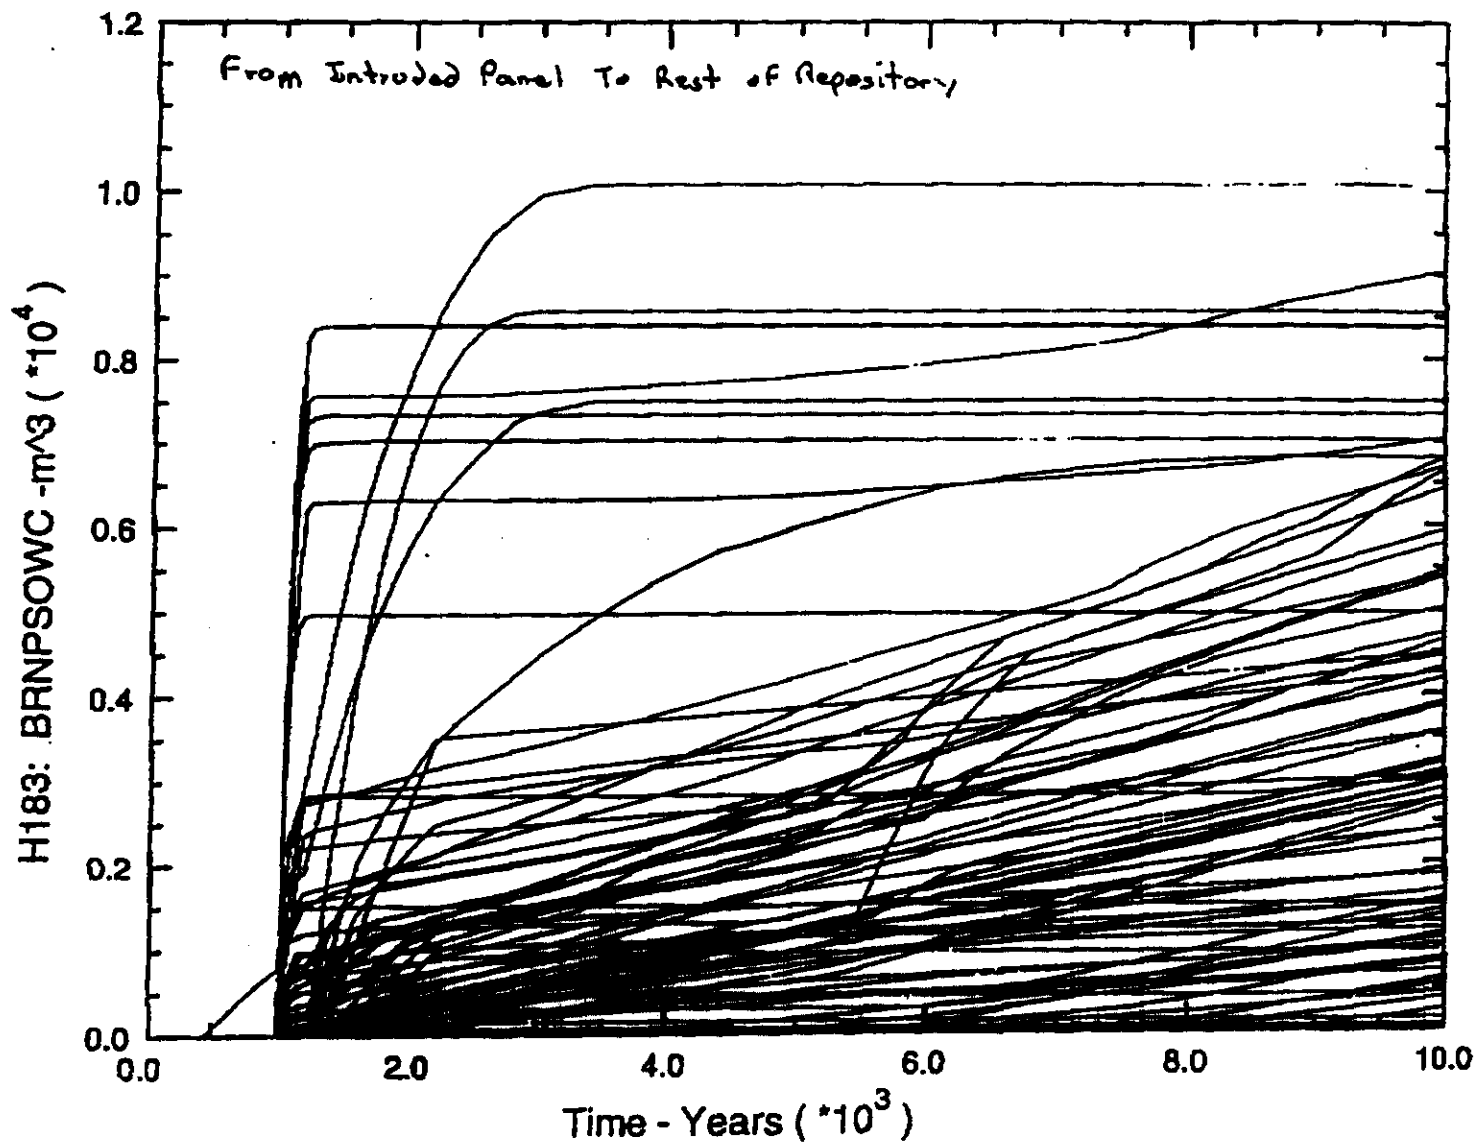


Figure 5: Cumulative flows between a panel and the rest of the repository for an E1 Intrusion at 1000 Years

SNL WIPP PA96: BRAGFLO SIMULATIONS (CCA R1 S3 Vector 25)

Net Brine Inflow across Panel Seal into Rest of Repository

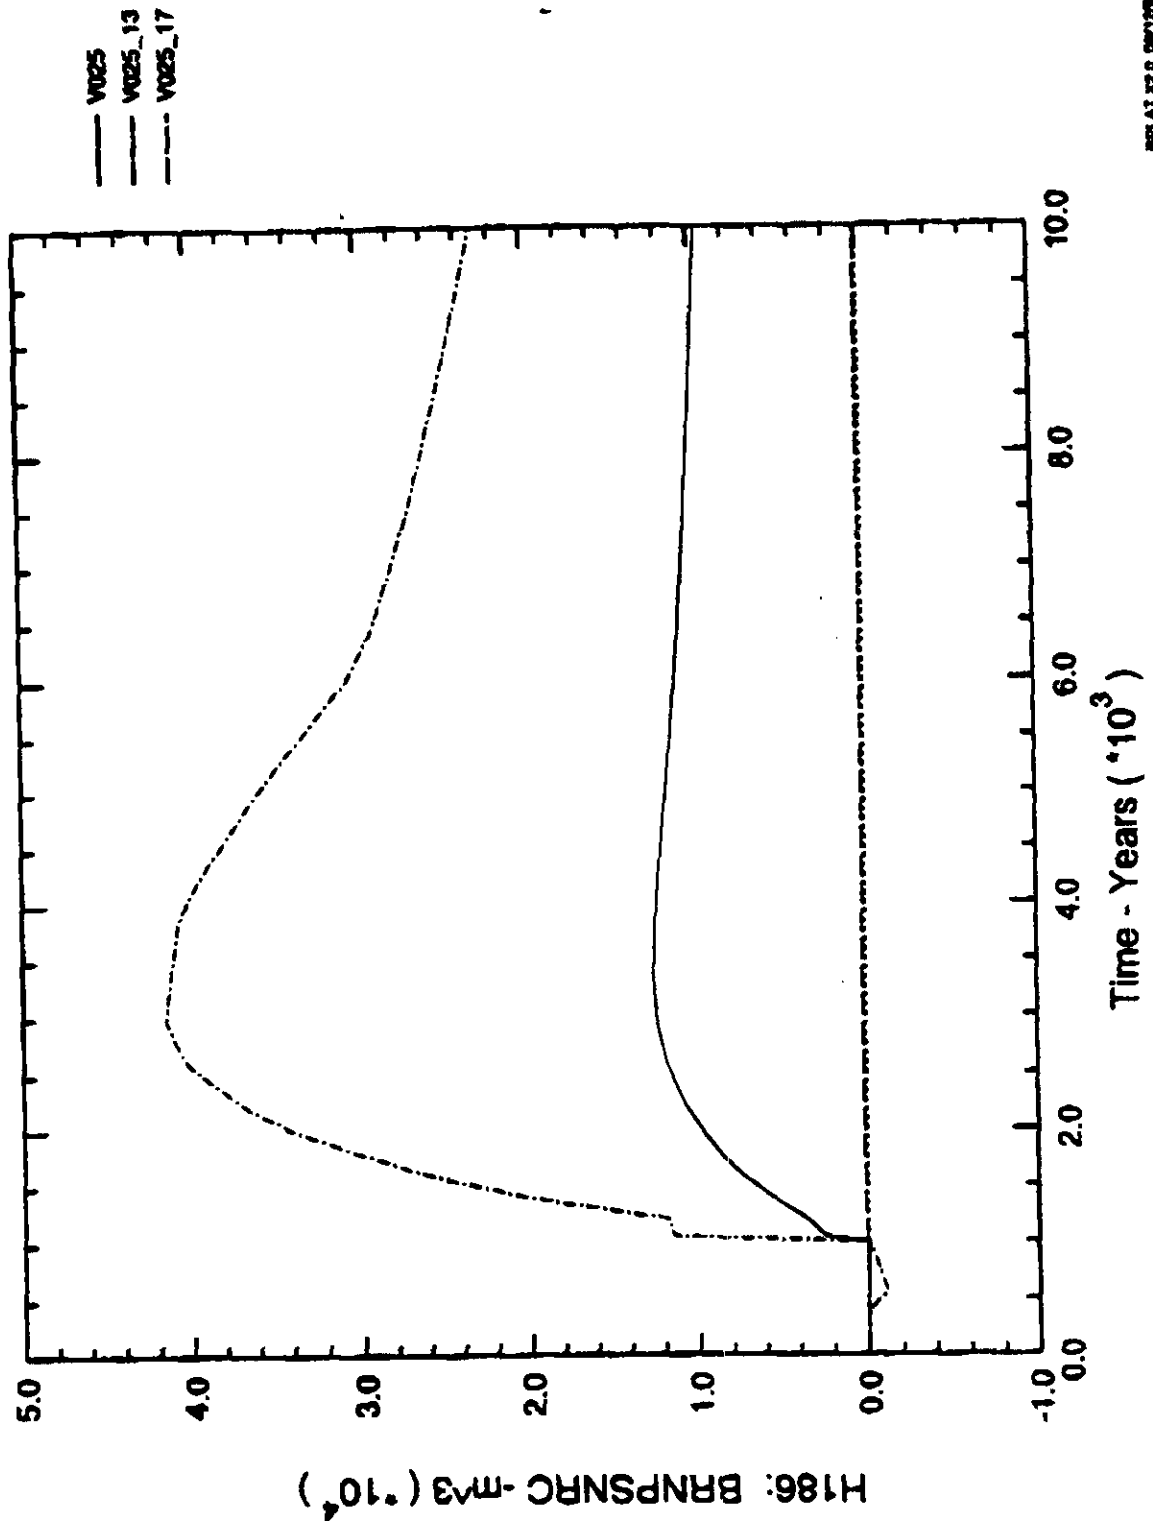


Figure 6: Cumulative flows through the Panel Closures for Permeabilities of 10⁻¹⁵ to 10⁻¹⁷ m². Results shown are for the Maximum Flow Case of Figure 5.